

Thermal conductivity of compressed earth blocks produced with recycled cement

M. Glória Gomes^{1*}, J. Alexandre Bogas¹, S. Real¹, R. Cruz¹

¹CERIS, Instituto Superior Técnico, Universidade de Lisboa, Av. Rovisco Pais, 1049-001 Lisbon, Portugal

Keywords: Compressed earth blocks; recycled cement; thermal conductivity

Presenting author email*: maria.gloria.gomes@tecnico.ulisboa.pt

Earth building materials have been exploited in construction for centuries, due to its production simplicity, reduced embodied energy and carbon footprint as well as its good hygrothermal comfort (Walker, 2004). In particular, their thermal conductivity has been reported to be as low as 0.26 W/mK (Adam and Jones, 1995), proving to be a material with good insulation capacity. However, with the development of more robust building materials, such as concrete, it fell into disuse (Riza *et al.*, 2010).

In the last decades, the growing concern with sustainability and the emergence of new construction techniques, namely mechanical and chemical stabilisation, to improve their performance and address some of their main issues (reduced water resistance), has brought a new momentum to earth construction (Riza *et al.*, 2010). Chemical stabilisation of compressed earth blocks (CEB) is usually achieved with the incorporation of hydraulic binders, namely ordinary Portland cement (PC). Though it is effective in improving the overall performance of CEB (Walker, 2004; Riza *et al.*, 2010), PC is a carbon intensive building material, associated with the consumption of large quantities of natural resources and energy, as well as, with the emission of copious amounts of carbon dioxide and other harmful green-house gases (Real *et al.*, 2022).

Recently, a new promising binder has been developed as a more eco-efficient alternative to PC, thermoactivated recycled cement (RC), which is produced from recycled construction and demolition waste materials subjected to thermal activation at lower temperatures than PC (about 600-700°C), thus, not only avoiding natural resource consumption and recycling waste, but also having reduced CO₂ emissions during production (Real *et al.*, 2022). RC has been successfully incorporated in other building materials, such as pastes, mortars and concrete (Real *et al.*, 2020; Carriço *et al.*, 2022; Real *et al.*, 2021; Carriço *et al.*, 2021). However, the effect of its use as a stabiliser on the performance of CEB has yet to have been assessed. Therefore, this study aims to analyse the influence of the incorporation of RC in the thermal conductivity of CEB. To this end, CEB were produced with different types of RC (recycled cement produced from cement paste waste treated at 650°C) and PC and amounts of stabiliser (5-10%), as well as unstabilised CEB (UCEB), as presented in Table 1. The tests were performed using through a modified transient pulse method (ASTM D5334, 2014; ASTM D5930, 2009), resorting to an *ISOMET 2114* heat transfer analyser with a surface probe (Figure 1), from *Applied Precision Enterprise*. The CEB were tested under varying moisture conditions, namely in laboratory conditions and in the dry and saturated states.

Table 1 – Composition of CEB

Designation	Soil ^{a)} (%)	PC ^{b)} (%)	RC ^{b)} (%)	Water ^{c)} (%)
PC10	90	10	-	15.0
RC10	90	-	10	16.5
PC5	95	5	-	15.2
RC5	95	-	5	16.5
RC2PC8	90	8	2	15.0
RC5PC5	90	5	5	15.5
UCEB	100	-	-	14.4

^{a)} Soil with 4% humidity; ^{b)} By weight of solids (soil+stabiliser); ^{c)} Total w/b (water/binder), including water absorbed by soil

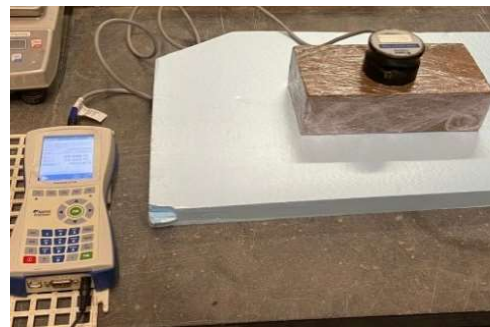


Figure 1 – Thermal conductivity test setup

Figure 2 presents the thermal conductivity of the tested CEB. As expected, the thermal conductivity tended to increase with the moisture content, given that the thermal conductivity of water is about 25 times higher than that of air (Ashworth and Ashworth, 1991). The thermal conductivity of the CEB in the saturated state was more than twice as high as those in the dry state, displaying a significant loss of thermal insulation capacity. Hall and Casey (2012) also pointed out this aspect. In fact, the effect of the moisture content was more relevant to the thermal conductivity than other parameters, such as the type and amount of stabiliser.

The CEB stabilised with RC displayed lower thermal conductivities than CEB stabilised with PC or UCEB. This should be due to the higher porosity associated to the CEB with RC, which were produced with a higher amount of water to account for the higher water demand and porosity of this stabiliser.

Figure 3 relates the thermal conductivity in the dry state with the total porosity of the CEB. A high correlation was found between these properties, demonstrating that the thermal conductivity is essentially influenced by the porosity of the CEB. This was expected, given that the thermal conductivity of building materials can be directly related to their porosity and density (Real *et al.*, 2016).

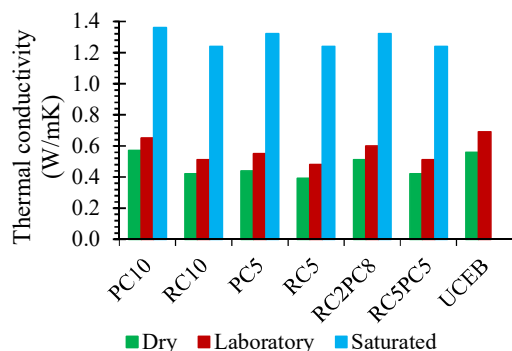


Figure 2 – Thermal conductivity of studied CEB

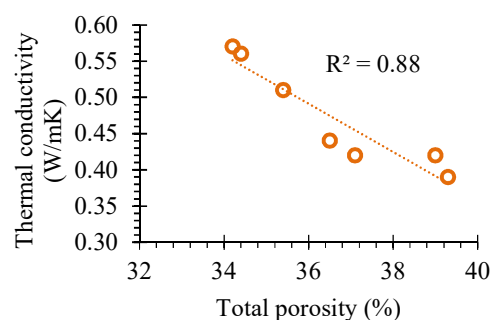


Figure 3 – Thermal conductivity in the dry state vs total porosity of CEB

Acknowledgements

The authors wish to thank the Portuguese Foundation for Science and Technology (FCT) for funding this research under project Eco+RCEB, ref. PTDC/ECI-CON/0704/2021, and under unit project UIDB/ECI/04625/2020 (CERIS), as well as Oficinas do Convento, Montemor, and SECIL for supporting the experimental work.

References

- Adam EA, Jones PJ (1995) Thermophysical properties of stabilised soil building blocks. *Building and Environment* 30(2) 245-253. [https://doi.org/10.1016/0360-1323\(94\)00041-P](https://doi.org/10.1016/0360-1323(94)00041-P)
- Ashworth T, Ashworth E (1991) Thermal conductivity of several concretes as a function of moisture. In *Insulation Materials: Testing and Applications* (Graves RS and Wysocki DC (eds)). ASTM International, West Conshohocken, PA, USA, STP 1116, pp. 415–429.
- ASTM (2014) D5334-14: Standard test method for determination of thermal conductivity of soil and soft rock by thermal needle probe procedure. ASTM International, West Conshohocken, PA, USA.
- ASTM (2009) D5930-09: Standard test method for thermal conductivity of plastics by means of a transient line-source technique. ASTM International, West Conshohocken, PA, USA.
- Carriço A, Real S, Bogas JA (2021). Durability performance of thermoactivated recycled cement concrete. *Cement and Concrete Composites*, 124, 104270. <https://doi.org/10.1016/j.cemconcomp.2021.104270>
- Carriço A, Bogas JA, Real S, Pereira MFC (2022) Shrinkage and sorptivity of mortars with thermoactivated recycled cement. *Construction and Building Materials* 333, 127392. <https://doi.org/10.1016/j.conbuildmat.2022.127392>
- Hall MR, Casey S (2012) Hygrothermal behaviour and occupant comfort in modern earth buildings. In *Modern Earth Buildings. Materials, engineering, construction and applications*. 1st Edition, Materials, Engineering, Constructions and Applications, Chapter 2. Edited by Hall M, Lindsay R and Krayenhoff M. Woodhead Publishing Limited.
- Real S, Bogas JA, Gomes MG, Ferrer B (2016) Thermal conductivity of structural lightweight aggregate concrete. *Magazine of Concrete Research* 68(15), 798–808. <http://dx.doi.org/10.1680/jmacr.15.00424>
- Real S; Carriço A, Bogas J, Guedes M (2020) Influence of the treatment temperature on the microstructure and hydration behavior of thermoactivated recycled cement. *Materials* 13(18), 3937. <https://doi.org/10.3390/ma13183937>
- Real S, Bogas JA, Carriço A (2021) Mechanical characterisation and shrinkage of thermoactivated recycled cement concrete. *Applied Sciences* 11, 2454. <https://doi.org/10.3390/app11062454>
- Real S, Sousa V, Meireles I, Bogas JA, Carriço A. (2022) Life cycle assessment of thermoactivated recycled cement production. *Materials* 15, 6766. <https://doi.org/10.3390/ma15196766>
- Riza FV, Rahman IA, Zaidi AMA (2010) A brief review of compressed stabilized earth brick (CSEB). In *2010 International Conference on Science and Social Research (CSSR 2010)*. <https://doi.org/10.1109/CSSR.2010.5773936>
- Walker PJ (2004) Strength and erosion characteristics of earth blocks and earth block masonry. *Journal of Materials in Civil Engineering* 16(5), 497-506. [https://doi.org/10.1061/\(ASCE\)0899-1561\(2004\)16:5\(497\)](https://doi.org/10.1061/(ASCE)0899-1561(2004)16:5(497))